

DIVERSIFIED
TESTING LABORATORIES, INC.
WORLDWIDE SERVICE

"We Test Per Your Request"

336 WEST FRONT STREET
P.O. BOX 4004
BURLINGTON, NORTH CAROLINA 27215
PHONE (336) 227-7710 • FAX (336) 227-1175
www.diversifiedtestinglabs.com

December 17, 2025

Mr. Kevin Jones
RICHLOOM FABRICS GROUP
100 Bailey Plant Road
Clinton, NC 29325

Reference: Laboratory Test Report
Lab Identification No. 66600
Invoice No. 97863

Dear Mr. Jones:

One (1) fabric sample, identified as **Tisket Alpaca (Stain Repellent and Backing)**, was received and tested in accordance with the test procedures outlined. The results are as follows:

Test Results


<u>Test Procedures</u>	<u>Warp</u>	<u>Fill</u>
Breaking Strength (lbf) ASTM D 5034-21 (Grab)	455.8	141.3
Yarn Slippage (lbf) ASTM D 4034-19	86.4	85.1
Resistance to Pilling ASTM D 3511-16 (Brush)	4.5 – Slight Pilling 4 – Slight Fuzzing	
Surface Abrasion ASTM D 4157-13 (#10 Cotton Duck Abradant) 4lb. Tension, 3lb. Load	Passed 54,000 Cycles	

Sincerely,

Brian S. Dement

BSD/mr



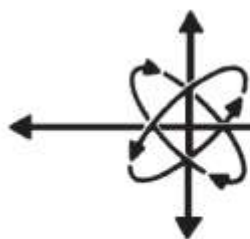

DIVERSIFIED
TESTING LABORATORIES, INC.
WORLDWIDE SERVICE

"We Test Per Your Request"

336 WEST FRONT STREET
P.O. BOX 4004
BURLINGTON, NORTH CAROLINA 27215
PHONE (336) 227-7710 • FAX (336) 227-1175
www.diversifiedtestinglabs.com

December 17, 2025

Mr. Kevin Jones
RICHLOOM FABRICS GROUP
100 Bailey Plant Road
Clinton, NC 29325

Reference: Laboratory Test Report
Lab Identification No. 66600
Invoice No. 97863

Dear Mr. Jones:

One (1) fabric sample, identified as **Tisket Alpaca (Stain Repellent and Backing)**, was received and tested in accordance with the California Technical Bulletin 117-2013, Section 1, Cover Fabric Test. The results are as follows:

Test Results

<u>Vertical Char Lengths</u>		
18mm	20mm	18mm


The sample submitted **meets** the requirements of the above standard. There were no ignitions or smoldering after 45 minutes on any of the three specimens tested. In addition, none of the three test specimens displayed a char which was greater than 45 mm.

Sincerely,

Brian S. Dement

BSD/mr



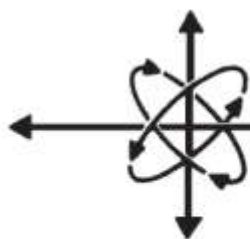

DIVERSIFIED
TESTING LABORATORIES, INC.
WORLDWIDE SERVICE

"We Test Per Your Request"

336 WEST FRONT STREET
P.O. BOX 4004
BURLINGTON, NORTH CAROLINA 27215
PHONE (336) 227-7710 • FAX (336) 227-1175
www.diversifiedtestinglabs.com

December 17, 2025

Mr. Kevin Jones
RICHLOOM FABRICS GROUP
100 Bailey Plant Road
Clinton, NC 29325

Reference: Laboratory Test Report
Lab Identification No. 66600
Invoice No. 97863

Dear Mr. Jones:

One (1) fabric sample, identified as **Tisket Alpaca (Stain Repellent and Backing)**, was received and tested in accordance with the NFPA 260, "Cigarette Ignition Resistance of Components of Upholstered Furniture, 2019 Edition", (Cover Fabric Test). The results are as follows:

Test Results

Vertical Char Lengths

20mm

20mm

20mm

*Date Tested: December 16, 2025

*Conditioned minimum of 4 hours @ 70±5°F and >65% RH


The sample submitted **meets** the requirements of the above standard and may be considered a **Class I Cover Fabric**. There were no ignitions on any of the three specimens tested. In addition, none of the three test specimens displayed a vertical char which was equal to or greater than 45 mm.

Sincerely,

Brian S. Dement

BSD/mr



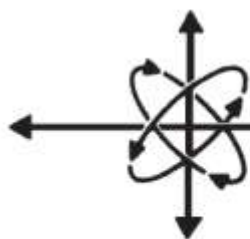

DIVERSIFIED
TESTING LABORATORIES, INC.
WORLDWIDE SERVICE

“We Test Per Your Request”

336 WEST FRONT STREET
P.O. BOX 4004
BURLINGTON, NORTH CAROLINA 27215
PHONE (336) 227-7710 • FAX (336) 227-1175
www.diversifiedtestinglabs.com

Lab Identification No. 66600

Sample Identification: **Tisket Alpaca (Stain Repellent and Backing)**

